



Spin-Orbit-Enhanced Functionality in $\text{LaAlO}_3/\text{SrTiO}_3$ Nanostructures

Jeremy Levy
UNIVERSITY OF PITTSBURGH

09/16/2015
Final Report

DISTRIBUTION A: Distribution approved for public release.

Air Force Research Laboratory
AF Office Of Scientific Research (AFOSR)/ RTB1
Arlington, Virginia 22203
Air Force Materiel Command

REPORT DOCUMENTATION PAGE				<i>Form Approved</i> OMB No. 0704-0188	
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to the Department of Defense, Executive Service Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.</p>					
1. REPORT DATE (DD-MM-YYYY)		2. REPORT TYPE Final Report		3. DATES COVERED (From - To) June 15, 2012 --June 14, 2015	
4. TITLE AND SUBTITLE Spin-Orbit-Lattice Coupling in LaAlO ₃ /SrTiO ₃ Nanostructures				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER FA9550-12-1-0268	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Jeremy Levy Patrick Irvin				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of Pittsburgh				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) Air Force Office of Scientific Research				10. SPONSOR/MONITOR'S ACRONYM(S) AFOSR	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT DISTRIBUTION A					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT <p>The overarching goal of the proposed research has been to develop a fundamental understanding of conductive nanostructures at oxide interfaces, and in particular to explore the role of spin-orbit interactions. We have used a variety of methods to work toward this goal, including the use of DC-GHz transport and optical techniques as well as exploration of alternative growth methods. Below we focus on several key results that are representative of our findings.</p>					
15. SUBJECT TERMS Oxide nanoelectronics, spin-orbit coupling.					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON Jeremy Levy
a. REPORT	b. ABSTRACT	c. THIS PAGE			19b. TELEPHONE NUMBER (Include area code) 412-624-2736

INSTRUCTIONS FOR COMPLETING SF 298

1. REPORT DATE. Full publication date, including day, month, if available. Must cite at least the year and be Year 2000 compliant, e.g. 30-06-1998; xx-06-1998; xx-xx-1998.

2. REPORT TYPE. State the type of report, such as final, technical, interim, memorandum, master's thesis, progress, quarterly, research, special, group study, etc.

3. DATES COVERED. Indicate the time during which the work was performed and the report was written, e.g., Jun 1997 - Jun 1998; 1-10 Jun 1996; May - Nov 1998; Nov 1998.

4. TITLE. Enter title and subtitle with volume number and part number, if applicable. On classified documents, enter the title classification in parentheses.

5a. CONTRACT NUMBER. Enter all contract numbers as they appear in the report, e.g. F33615-86-C-5169.

5b. GRANT NUMBER. Enter all grant numbers as they appear in the report, e.g. AFOSR-82-1234.

5c. PROGRAM ELEMENT NUMBER. Enter all program element numbers as they appear in the report, e.g. 61101A.

5d. PROJECT NUMBER. Enter all project numbers as they appear in the report, e.g. 1F665702D1257; ILIR.

5e. TASK NUMBER. Enter all task numbers as they appear in the report, e.g. 05; RF0330201; T4112.

5f. WORK UNIT NUMBER. Enter all work unit numbers as they appear in the report, e.g. 001; AFAPL30480105.

6. AUTHOR(S). Enter name(s) of person(s) responsible for writing the report, performing the research, or credited with the content of the report. The form of entry is the last name, first name, middle initial, and additional qualifiers separated by commas, e.g. Smith, Richard, J, Jr.

7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES). Self-explanatory.

8. PERFORMING ORGANIZATION REPORT NUMBER. Enter all unique alphanumeric report numbers assigned by the performing organization, e.g. BRL-1234; AFWL-TR-85-4017-Vol-21-PT-2.

9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES). Enter the name and address of the organization(s) financially responsible for and monitoring the work.

10. SPONSOR/MONITOR'S ACRONYM(S). Enter, if available, e.g. BRL, ARDEC, NADC.

11. SPONSOR/MONITOR'S REPORT NUMBER(S). Enter report number as assigned by the sponsoring/monitoring agency, if available, e.g. BRL-TR-829; -215.

12. DISTRIBUTION/AVAILABILITY STATEMENT. Use agency-mandated availability statements to indicate the public availability or distribution limitations of the report. If additional limitations/ restrictions or special markings are indicated, follow agency authorization procedures, e.g. RD/FRD, PROPIN, ITAR, etc. Include copyright information.

13. SUPPLEMENTARY NOTES. Enter information not included elsewhere such as: prepared in cooperation with; translation of; report supersedes; old edition number, etc.

14. ABSTRACT. A brief (approximately 200 words) factual summary of the most significant information.

15. SUBJECT TERMS. Key words or phrases identifying major concepts in the report.

16. SECURITY CLASSIFICATION. Enter security classification in accordance with security classification regulations, e.g. U, C, S, etc. If this form contains classified information, stamp classification level on the top and bottom of this page.

17. LIMITATION OF ABSTRACT. This block must be completed to assign a distribution limitation to the abstract. Enter UU (Unclassified Unlimited) or SAR (Same as Report). An entry in this block is necessary if the abstract is to be limited.

Final Report

Spin-Orbit-Lattice Coupling in $\text{LaAlO}_3/\text{SrTiO}_3$ Nanostructures FA9550-12-1-0268

Principal Investigator: Jeremy Levy

Department of Physics and Astronomy, University of Pittsburgh

3941 O'Hara St., Pittsburgh, PA 15260 USA

Tel: 412-624-2736, Fax: 412-624-9163

Email: jlevy@pitt.edu

Co-Principal Investigator: Patrick Irvin

Department of Physics and Astronomy, University of Pittsburgh

3941 O'Hara St., Pittsburgh, PA 15260 USA

Tel: 412-624-2730

Email: prist2@pitt.edu

Publications:

- G. Jnawali, L. Chen, M. Huang, H. Lee, S. Ryu, J. P. Podkaminer, C.-B. Eom, P. Irvin, and J. Levy, "Photoconductive response of a single Au nanorod coupled to LaAlO₃/SrTiO₃ nanowires," *Applied Physics Letters* **106**, 211101 (2015).
<http://dx.doi.org/10.1063/1.4921750>
- A. Levy, F. Bi, M. Huang, S. Lu, M. Tomczyk, G. Cheng, P. Irvin, and J. Levy, "Writing and Low-Temperature Characterization of Oxide Nanostructures," *J. Vis. Exp.* **89**, e51886 (2014). <http://dx.doi.org/doi:10.3791/51886>
- J. A. Sulpizio, S. Ilani, P. Irvin, and J. Levy, "Nanoscale Phenomena in Oxide Heterostructures," *Annual Review of Materials Research* **44**, 117 (2014). <http://dx.doi.org/10.1146/annurev-matsci-070813-113437>
- J. P. Podkaminer, T. Hernandez, M. Huang, S. Ryu, C. W. Bark, S. H. Baek, J. C. Frederick, T. H. Kim, K. H. Cho, J. Levy, M. S. Rzchowski, and C. B. Eom, "Creation of a two-dimensional electron gas and conductivity switching of nanowires at the LaAlO₃/SrTiO₃ interface grown by 90° off-axis sputtering," *Applied Physics Letters* **103**, 071604 (2013).
<http://dx.doi.org/10.1063/1.4817921>
- Y. Ma, M. Huang, S. Ryu, C. W. Bark, C.-B. Eom, P. Irvin, and J. Levy, "Broadband Terahertz generation and detection at 10 nm scale," *Nano Letters* **13**, 2884 (2013).
<http://dx.doi.org/10.1021/nl401219v>
- P. Irvin, M. Huang, F. J. Wong, T. D. Sanders, Y. Suzuki, and J. Levy, "Gigahertz-frequency operation of a LaAlO₃/SrTiO₃-based nanotransistor," *Applied Physics Letters* **102**, 103113 (2013). <http://dx.doi.org/10.1063/1.4795725>

Presentations

- Ultrafast Optical Response of Graphene/LaAlO₃/SrTiO₃ Nanostructures. Chen, Lu; Jnawali, Giriraj; Huang, Mengchen; Hsu, Jen-Feng; Bi, Feng; Lee, Hyungwoo; Ryu, Sangwoo; Eom, Chang-Beom; D'Urso, Brian; Irvin, Patrick; Levy, Jeremy. APS March Meeting 2015, abstract #L13.001
- Electric field effects in graphene-complex-oxide heterostructures. Jnawali, Giriraj; Huang, Mengchen; Hsu, Jen-Feng; Bi, Feng; Chen, Lu; Zhou, Rongpu; Lee, Hyungwoo; Ryu, Sangwoo; Eom, Chang-Beom; Irvin, Patrick; D'Urso, Brian; Levy, Jeremy. APS March Meeting 2015, abstract #S16.011
- Anisotropic superconducting properties of nanowires at the LaAlO₃/SrTiO₃ (110) interface. Irvin, Patrick; Huang, Mengcheng; Annadi, Anil; Cheng, Guanglei; Levy, Jeremy; Gopinadhan, Kalon; Venkatesan, Thirumalai; Ariando, Ariando. APS March Meeting 2015, abstract #L13.009
- Quantized conductance through quantum point contacts in LaAlO₃/SrTiO₃ nanowires. Annadi, Anil; Lu, Shicheng; Cheng, Guanglei; Tomczyk, Michelle; Huang, Mengchen; Lee, Hyungwoo; Ryu, Sangwoo; Eom, Chang-Beom; Irvin, Patrick; Levy, Jeremy. APS March Meeting 2015, abstract #L13.007
- Quantized conductance through reconfigurable 1D channels. Lu, Shicheng; Annadi, Anil; Cheng, Guanglei; Tomczyk, Michelle; Huang, Mengchen; Lee, Hyungwoo; Ryu, Sangwoo; Eom, Chang-Beom; Irvin, Patrick; Levy, Jeremy. APS March Meeting 2015, abstract #M26.014
- THz investigations of graphene-complex-oxide heterostructures. Jnawali, Giriraj; Chen, Lu; Irvin, Patrick; Levy, Jeremy; Ryu, Sangwoo; Eom, Chang-Beom; Ghahari, Fereshte; Ravichandran, Jayakanth; Kim, Philip. APS March Meeting 2014, abstract #Y45.00013
- Broadband THz Spectroscopy of Single Nanoscale Objects. Lu Chen, Giriraj Jnawali, Mengchen Huang, Patrick Irvin, Sangwoo Ryu, Chang-Beom Eom, Jeremy Levy. APS March Meeting 2014, abstract #T44.00008
- Broadband THz Generation and Detection at 10 nm Scale. Yanjun Ma , Mengchen Huang , Jeremy Levy, Sangwoo Ryu, Chung Wung Bark, Chang-Beom Eom. APS March Meeting 2013, abstract #C12.00010
- Ultrafast photoresponse of oxide nanostructures. Lu Chen , Yanjun Ma , Mengchen Huang , Sangwoo Ryu , Chung Wung Bark , Chang-Beom Eom , Jeremy Levy. APS March Meeting 2013, abstract #C12.00002

Major Accomplishments

The overarching goal of the proposed research has been to develop a fundamental understanding of conductive nanostructures at oxide interfaces, and in particular to explore the role of spin-orbit interactions. We have used a variety of methods to work toward this goal, including the use of DC-GHz transport and optical techniques as well as exploration of alternative growth methods. Below we focus on several key results that are representative of our findings.

Spin-orbit effects in 1D/2D nanostructures

The role of spin-orbit interactions depends crucially on the dimensionality of the system. The LaAlO₃/SrTiO₃ interface is already intrinsically two-dimensional; however, we utilize a conductive-AFM lithography technique to produce conductive nanostructures on the scale of 10 nm and smaller. Figure 1 (top) shows an illustration of a structure that was designed to explore the role of dimensionality on spin-

orbit interactions. The device has five leads, two of which are used to source current (along the horizontal), and three of which are used to measure voltage drops along two channels, one of which is quasi-1D and the other of which is much wider. The 1D segment has a width $w \sim 10$ nm, as measured by nanowire erasure experiments. The 2D segment is created by raster-scanning a rectangular area that is 200 nm wide. Transport experiments are performed as a function of a plane-perpendicular magnetic field up to 50 kOe, and as a function of an applied back gate voltage V_{back} . We observe a clear crossover from 2D weak antilocalization to a 1D suppression of this effect due to depletion from V_{back} in the 2D channel. At the most negative back gate voltage, the 1D and 2D magnetotransport results look almost identical, while there is clear weak antilocalization for the 2D system at positive back gate voltages. These results are being compared with tight-binding calculations to provide a quantitative estimate for the spin-orbit interactions in this system.

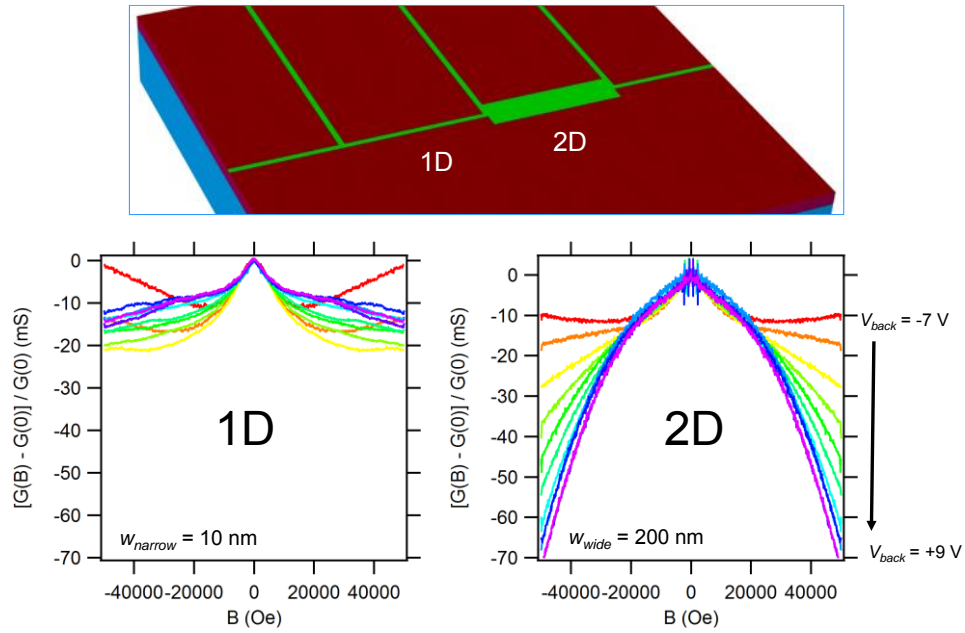


Figure 1. 1D/2D Crossover of Spin-Orbit Coupling in $\text{LaAlO}_3/\text{SrTiO}_3$ Heterostructures

THz spectroscopy of nanoparticles

We have pursued the development and use of ultrafast optical techniques to probe the interactions of conductive nanostructures at THz frequencies {Jnawali, 2015 #2999}. Figure 2 (top left) shows an AFM image of a LAO/STO canvas on which single Au nanorods (AuNRs) have been dispersed. These nanorods have plasmonic resonances that locally enhance the optical fields excited by near-infrared pulsed laser illumination. In this particular experiment, a single AuNR is identified by AFM and placed as a nanojunction. The full nanowire topology is indicated by white dashed lines, and the green triangular-shaped regions represent areas where electrical contact to interface is maximized. The use of four terminals allows for an enhancement of optically induced electrical signals. The plasmonic resonance for these AuNRs is shown directly below: a 100 nm-wide plasmonic resonance, centered around 810 nm, exists for these structures collectively. Using our time-resolved microscopy technique, we can focus on this single AuNR and measure the photoconductive response as a function of position and polarization. The results are shown in Figure 2(b-e), in which there is significant polarization contrast due to the aspect ratio of the AuNR, and the spectral response shows a similar selectivity. THz spectroscopy can in

principle be applied to any molecular-scale object placed on the LAO/STO canvas. Alternately, this technique can be used to probe the far-infrared response of LAO/STO, an energy range that is difficult to access using other techniques but is important for understanding spin-orbit couplings (whose energies are also on a similar scale).

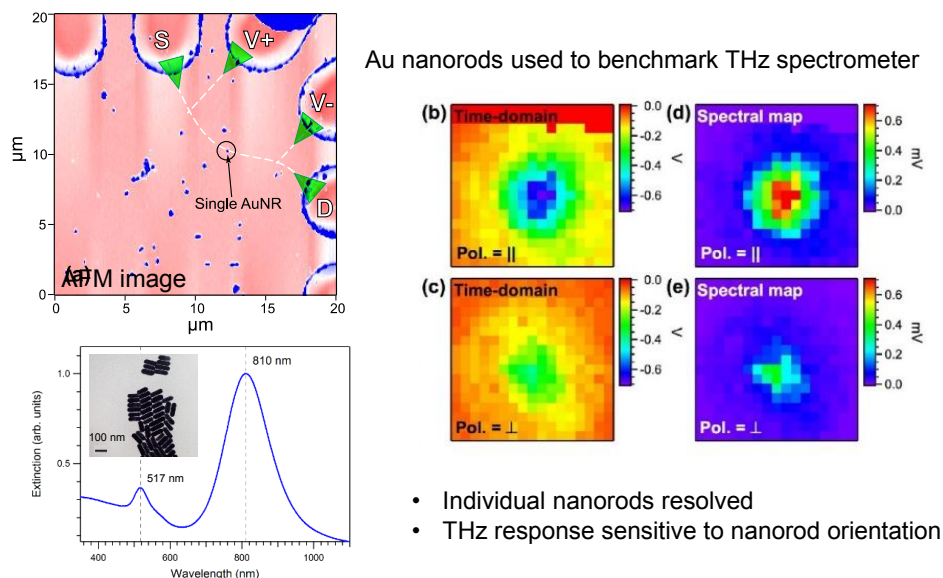


Figure 2. Platform for molecular-scale THz spectroscopy.

Broadband Terahertz generation and detection at 10 nm scale

Terahertz (0.1–30 THz) radiation reveals a wealth of information that is relevant for material, biological, and medical sciences with applications that span chemical sensing, high-speed electronics, and coherent control of semiconductor quantum bits. We have reported {Irvin, 2013 #1245} both generation and detection of broadband terahertz field from 10 nm scale oxide nanojunctions. Frequency components of ultrafast optical radiation are mixed at these nanojunctions, producing broadband THz emission. These same devices detect THz electric fields with comparable spatial resolution. This unprecedented control, on a scale of 4 orders of magnitude smaller than the diffraction limit, creates a pathway toward THz-bandwidth spectroscopy and control of individual nanoparticles and molecules.


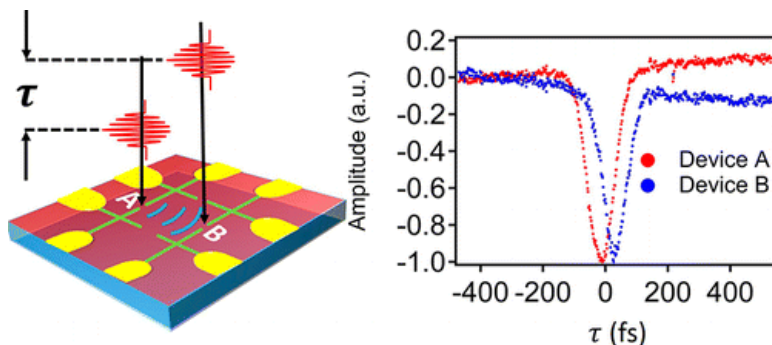


Figure 3. Nanometer-scale generation and detection of broadband THz emission.

Gigahertz-frequency operation of a $\text{LaAlO}_3/\text{SrTiO}_3$ -based nanotransistor

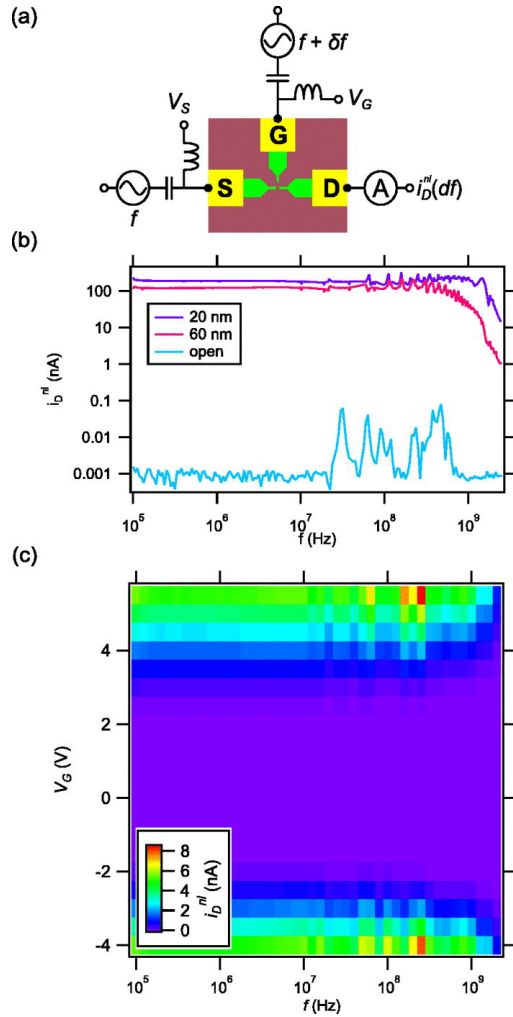

Nanoscale control of the metal-insulator transition of the $\text{LaAlO}_3/\text{SrTiO}_3$ interface with a conductive-atomic force microscope (c-AFM) technique has enabled a variety of electrical and photonic device concepts. While previous devices have demonstrated sub-10 nm critical features, information processing applications also require high operating speeds. We have shown that a “sketched” nanoscale transistor (“SketchFET”) can operate at frequencies in excess of 2 GHz. The combination of high speed and high conductance with a small footprint make these devices and this platform attractive for sub-10 nm computing and storage architectures.

Figure 4. GHz-frequency operation of SketchFET transistor.

1.

1. Report Type

Final Report

Primary Contact E-mail

Contact email if there is a problem with the report.

jlevy@pitt.edu

Primary Contact Phone Number

Contact phone number if there is a problem with the report

4126242736

Organization / Institution name

University of Pittsburgh

Grant/Contract Title

The full title of the funded effort.

Spin-Orbit-Enhanced Functionality in LaAlO₃/SrTiO₃ Nanostructures

Grant/Contract Number

AFOSR assigned control number. It must begin with "FA9550" or "F49620" or "FA2386".

FA9550-12-1-0268

Principal Investigator Name

The full name of the principal investigator on the grant or contract.

Jeremy Levy

Program Manager

The AFOSR Program Manager currently assigned to the award

Harold Weinstock

Reporting Period Start Date

06/15/2012

Reporting Period End Date

06/14/2015

Abstract

The overarching goal of the proposed research has been to develop a fundamental understanding of conductive nanostructures at oxide interfaces, and in particular to explore the role of spin-orbit interactions. We have used a variety of methods to work toward this goal, including the use of DC-GHz transport and optical techniques as well as exploration of alternative growth methods. Below we focus on several key results that are representative of our findings.

Distribution Statement

This is block 12 on the SF298 form.

Distribution A - Approved for Public Release

Explanation for Distribution Statement

If this is not approved for public release, please provide a short explanation. E.g., contains proprietary information.

SF298 Form

Please attach your SF298 form. A blank SF298 can be found [here](#). Please do not password protect or secure the PDF. The maximum file size for an SF298 is 50MB.

[AFD-070820-035.pdf](#)

DISTRIBUTION A: Distribution approved for public release.

Upload the Report Document. File must be a PDF. Please do not password protect or secure the PDF . The maximum file size for the Report Document is 50MB.

[BRI Final Report text.pdf](#)

Upload a Report Document, if any. The maximum file size for the Report Document is 50MB.

Archival Publications (published) during reporting period:

G. Jnawali, L. Chen, M. Huang, H. Lee, S. Ryu, J. P. Podkaminer, C.-B. Eom, P. Irvin, and J. Levy, "Photoconductive response of a single Au nanorod coupled to LaAlO₃/SrTiO₃ nanowires," Applied Physics Letters 106, 211101 (2015). <http://dx.doi.org/10.1063/1.4921750>

A. Levy, F. Bi, M. Huang, S. Lu, M. Tomczyk, G. Cheng, P. Irvin, and J. Levy, "Writing and Low-Temperature Characterization of Oxide Nanostructures," J. Vis. Exp. 89, e51886 (2014). <http://dx.doi.org/doi:10.3791/51886>

J. A. Sulpizio, S. Ilani, P. Irvin, and J. Levy, "Nanoscale Phenomena in Oxide Heterostructures," Annual Review of Materials Research 44, 117 (2014). <http://dx.doi.org/10.1146/annurev-matsci-070813-113437>

J. P. Podkaminer, T. Hernandez, M. Huang, S. Ryu, C. W. Bark, S. H. Baek, J. C. Frederick, T. H. Kim, K. H. Cho, J. Levy, M. S. Rzchowski, and C. B. Eom, "Creation of a two-dimensional electron gas and conductivity switching of nanowires at the LaAlO₃/SrTiO₃ interface grown by 90° off-axis sputtering," Applied Physics Letters 103, 071604 (2013). <http://dx.doi.org/10.1063/1.4817921>

Y. Ma, M. Huang, S. Ryu, C. W. Bark, C.-B. Eom, P. Irvin, and J. Levy, "Broadband Terahertz generation and detection at 10 nm scale," Nano Letters 13, 2884 (2013). <http://dx.doi.org/10.1021/nl401219v>

P. Irvin, M. Huang, F. J. Wong, T. D. Sanders, Y. Suzuki, and J. Levy, "Gigahertz-frequency operation of a LaAlO₃/SrTiO₃-based nanotransistor," Applied Physics Letters 102, 103113 (2013). <http://dx.doi.org/10.1063/1.4795725>

Changes in research objectives (if any):

Change in AFOSR Program Manager, if any:

Extensions granted or milestones slipped, if any:

AFOSR LRIR Number

LRIR Title

Reporting Period

Laboratory Task Manager

Program Officer

Research Objectives

Technical Summary

Funding Summary by Cost Category (by FY, \$K)

	Starting FY	FY+1	FY+2
Salary			
Equipment/Facilities			
Supplies			
Total			

Report Document

Report Document - Text Analysis

Report Document - Text Analysis

Appendix Documents

2. Thank You

E-mail user

DISTRIBUTION A: Distribution approved for public release.

Sep 03, 2015 15:22:48 Success: Email Sent to: jlevy@pitt.edu